

EFECTIS ERA AVRASYA

Fire Test Laboratory



Accredited Body No: AB-0556-T

CLASSIFICATION OF FIRE RESISTANCE PERFORMANCE IN ACCORDANCE WITH EN 13501-2:2016

Sponsor: DALSAN ALÇI SAN. VE TİC. A.Ş.

Kızılcaşar Mahallesi, 1184. Cadde, No:22/1 İncek, Gölbaşı,

Ankara / TURKEY

Prepared by: EFECTIS ERA AVRASYA Test ve Belgelendirme A.Ş.

DİLOVASI OSB. 5. Kısım Fırat Cad. 1. No:18 41455

Dilovası, Kocaeli / TURKEY

Product name: Suspended Ceiling System Consisting of Double Layers

of "A1 COREX 25 mm" Plasterboards

Classification

report No. : EEA-22-085

Issue number : 1/2

Date of issue : 11.08.2022

This classification report consists of 14 pages and may only be used or reproduced in its entirety.

Address: Dilovası OSB 5. Kısım Fırat Cad. No: 18 41455 Dilovası, Kocaeli / TURKEY Phone: 0262 6581662 Fax: 0262 6581669 E-mail: turkey@efectis.com

Web: www.efectis.com

1. INTRODUCTION

This classification report defines the classification in accordance with the procedures given in EN 13501-2:2016, assigned to 'Suspended Ceiling System Consisting of Double Layers of "A1 COREX 25 mm" Plasterboards'

2. DETAILS OF CLASSIFIED PRODUCT

2.1. General:

The element, 'Suspended Ceiling System Consisting of Double Layers of "A1 COREX 25 mm" Plasterboards', is defined as a type of product.

2.2. **Description:**

'Suspended Ceiling System Consisting of Double Layers of "A1 COREX 25 mm" Plasterboards', is fully described below.

2.2.1. General

Product identification: Suspended Ceiling System Consisting of Double Layers of "A1 COREX 25 mm"

Plasterboards

Direction of fire : Below the Suspended Ceiling System

Manufacturer : DALSAN ALÇI SAN. VE TİC. A.Ş.

Gebze Güzeller OSB İnönü Mah. Ziya Gökalp Cad. No: 4, 41400 Gebze,

Kocaeli / TURKEY

: DALSAN ALCI SAN. VE TİC. A.S. Sponsor of test

Kızılcaşar Mahallesi, 1184. Cadde, No:22/1 İncek, Gölbaşı, Ankara / TURKEY

2.2.2. Construction

Suspended Ceiling System Consisting of Double Layers of "A1 COREX 25 mm" Plasterboards were placed on bottom face of the framework.

Steel hangers were fixed to cement based concrete beams with a density of ca. 2000 kg/m³.

The supporting construction was supplied by the test laboratory (Efectis Era Avrasya) and consisted of aerated concrete blocks which have a nominal gross dry density of 600 kg/m³ and thickness of 200 mm. Total height of the supporting construction was 400 mm.

2.2.3. Components

2.2.3.1. Suspended Ceiling System

2.2.3.1.1. Hangers:

The framework was suspended by 28 pcs. of C type quick hanger. Hanger bars were fixed to concrete beams with steel dowels and L steel bars. Hanger bars were hanged on L steel bars and C-type quick hangers were placed to hanger bars which connected to TC galvanised steel profiles.

• Hanger: Galvanised Quick Hanger (C type) and hanger bar – DALSAN

Dimensions of quick hanger : See figure 8

Dimensions of hanger bar : 3,8 x 400 mm (Ø x L)

Fixing: Steel dowel with L steel bar and a nut - CD6-45 - DALSAN

: M6 x 45 mm (Ø x L) Dimensions : See figure 1, 2 and 3. Location

2.2.3.1.2. Framework

All edges of the supporting construction were circled by the U shaped galvanised steel profiles. Resilient tape was used between supporting construction and U shaped profiles. C shaped galvanised steel profiles were located in the U shaped galvanised steel profile crosswise.

U shaped galvanised steel profile - Ceiling U-track (TU) - DALSAN

Ceiling U-tracks were fixed to the supporting construction (side wall) by steel dowels.

- Dimensions : 3100/4100 x 28 x 27/27 x 0,5 mm (I x w x d x t)

Fixing : M6 x 45 mm (Ø x I) - CD6-45 - Steel dowel - DALSAN

 Location of fixing : 50 mm distance from edge of the supporting construction and

500 mm c.t.c distance between steel dowels.

C shaped galvanized steel profile – Ceiling C-stud (TC) – DALSAN

C shaped galvanised steel profiles were located in (without screws) the U shaped galvanised steel profiles.

- Dimensions : 3080 x 60 x 27/27 x 0,6 mm (l x w x h x t)

: The distance between each Ceilina C-stud is 600 mm. The studs had Location

10 mm gap between Ceiling U-track (TU) and Ceiling C-stud (TC)

Resilient tape:

Type : Sound resilient polyethylene foam tape – DALSAN

 $: 25 \times 3 \text{ mm (w x t)}$ o Dimensions

 Nominal density : 30 kg/m³

: Between supporting construction and U shaped profiles. Location

2.2.3.1.3. **Panels**

The suspended ceiling system have two layers of plasterboards. Plasterboards fixing to framework with self tapping screws screw. Joint tape and jointing compound were used at the joints of plasterboards. See figure 1, 5 and 6 for the layout of the panels.

Plasterboards – EN 15283-1, Type GM FH1R Plasterboard – A1 COREX 25 mm – DALSAN

Nominal Dimensions : 1200 x 2000 x 25 mm (w x l x t) - 2 layers.

Weight per unit area : 21,9 kg/m²

 Coating : Both faces of the plasterboards were covered with fiberglass

mattress; unit area weight of fiberglass mattress on one face of the

plasterboard 205 g/m².

Location : Plasterboards layers were staggered at bottom of the suspended

ceiling system

- Dimensions:

o First layer (inner layer):

: 250 x (1700+1400) mm (w x I), 1200 x (1400+1700) mm (w x I), 1200 x (1700+1400) mm (w x I), 1200 x (1400+1700) mm (w x I), 250 x (1700+1400) mm (w x I)

Second layer (outer layer):

: 850 x (1100+2000) mm (w x I), 1200 x (2000+1100) mm (w x I), Dimensions 1200 x (1100+2000) mm (w x I), 850 x (2000+1100) mm (w x I)

Fixing – Plasterboards fixing to framework with self tapping steel screws - DALSAN

Dimensions: : 3,5 x 45 mm (Ø x I) – COREX BV 45 - First layer

: 4,2 x 70 mm (Ø x I) - COREX BV 70 - Second layer

Location : At first layer the distance between screws is 300 mm and at second

layer the distance between screws is 150 mm

– Joints:

o Type : Joint compound - DERZTEK - DALSAN

 Wet density : 750 kg/m³

: Used at the joints of plasterboards at second layer. Location

Reinforcement: Joint tape – DALSAN

: Used at the joints of plasterboards at second layer. Joint tape

The joint tape was applied on the joints of the board

before the joint compound.

> Type : Self-adhesive fibre-glass tape.

> Nominal thickness: 0,13 mm Mass per unit area: 60 g/m²

For detailed information see figures 1-8.

3. REPORTS AND RESULTS IN SUPPORT OF CLASSIFICATION

3.1. **Reports**

Name of laboratory	Name of sponsor	Test report ref. no.	Test method		
EFECTİS ERA AVRASYA TEST VE BELGELENDİRME A.Ş.	DALSAN ALÇI SAN. VE TİC. A.Ş.	RFTR22118	EN 1364-2:2018		

3.2. Results

Test method	Parameter	Results
EN 1364-2:2018	Integrity, (E) - Cotton pad - Gap gauges Ø 6 mm Ø 25 mm - Flames longer than 10 sec.	no failure (not applied) no failure (not applied) no failure (not applied) not observed
	Insulation:, [I] - average temperature - maximum temperature	no failure no failure

The heating was terminated at 132nd minute after consulted with sponsor.

4. CLASSIFICATION AND FIELD OF APPLICATION

4.1. Reference of classification

This classification has been carried out in accordance with clause 7.5.4 of EN 13501-2:2016.

4.2. Classification

'Suspended Ceiling System Consisting of Double Layers of "A1 COREX 25 mm" Plasterboards' is classified according to the following combinations of performance parameters and classes:

R	Е	1	W		t	t	-	М	S	С	IncSlow	sn	ef	r
---	---	---	---	--	---	---	---	---	---	---	---------	----	----	---

FIRE RESISTANCE CLASSIFICATION

El120 (a←b)

4.3. Field of application

4.3.1 General

This report details the method of construction, the test conditions and the results obtained when the specific elements of construction described herein was tested following the procedure outlined in EN 1363-1:2020, and when appropriate EN 1363-2:1999. Any significant deviation with respect to size, constructional details, load stresses, edge or end conditions other than those allowed under the field of direct application in the relevant test method is not covered by this report.

4.3.2 Construction

The test results are directly applicable to an untested similar suspended ceiling construction provided the following is true:

4.3.2.1 With respect to size

Test results obtained on a test specimen of 4 m x 3 m or greater, may be applied to ceilings of any dimension, provided that the distribution per unit area of the hangers is not reduced and the distance between hangers is not increased. The distance between grid members and the load on the hanger, shall not be increased. Provisions for expansion in the ceiling system shall be increased pro rata with the extensions in sizes, while the gap at the perimeter shall be the same as tested.

4.3.2.2 With respect to fittings

Fittings which devices penetrating the ceilings that may be installed are those which have been included in the test specimen (example, lighting or ventilation etc.). The distance between the fittings cannot be smaller than tested.

4.3.2.3 With respect to cavity

The test results are valid for cavities of any height.

4.3.2.4 With respect to length of supporting hangers

The test results are applicable to ceilings suspended by hangers of any length.

4.3.2.5 With respect to cable, pipes, etc. above the ceiling

The test results are only applicable to the inclusion of cables, pipes, etc. above the ceiling provided they are installed in such a manner that they give no additional mechanical load to ceiling during the fire.

^{*} a: above, b: below

5. LIMITATIONS

This classification report does not represent any type approval or certification of the product. This report is initially valid until 11th August 2023 providing that no significant modifications are made in technical specification of the specimen and related test and classification standards

> Signed: Approved:

e-signed e-signed

Osman AYYILDIZ Onur DAĞ Chief Technical Officer Person in the charge of tests

6. DRAWINGS:

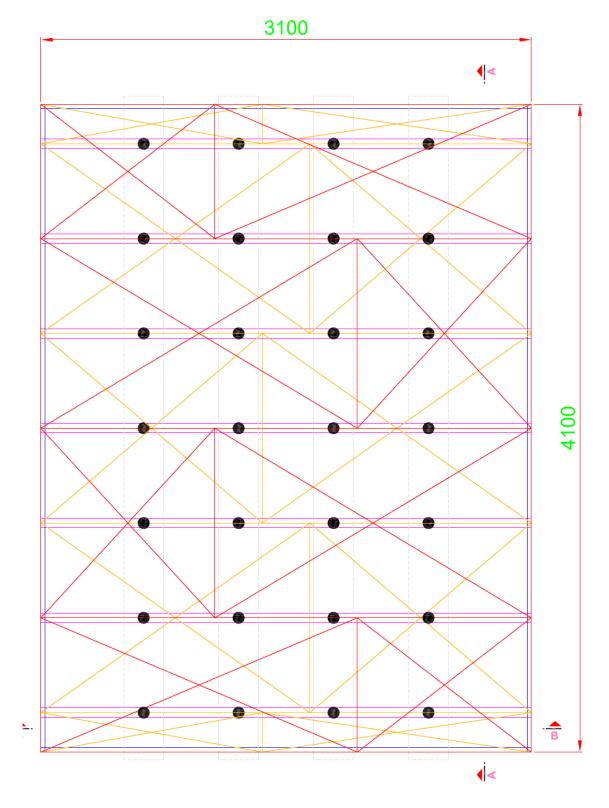


Figure 1: Suspended ceiling construction general view

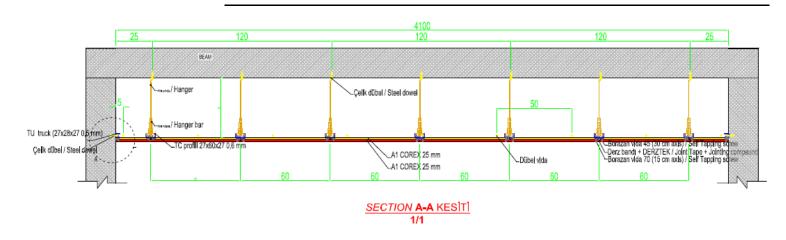


Figure 2: Cross section A-A view of the suspended ceiling construction

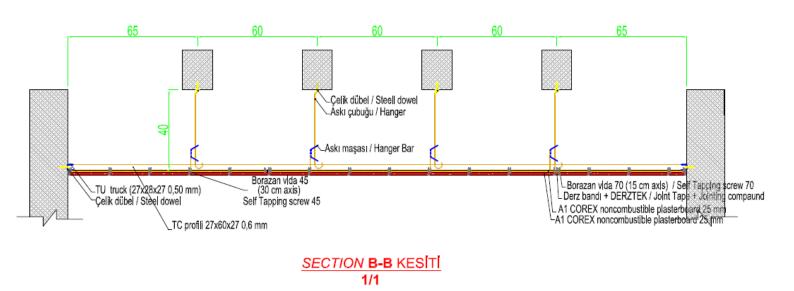


Figure 3: Cross section B-B view of the suspended ceiling construction

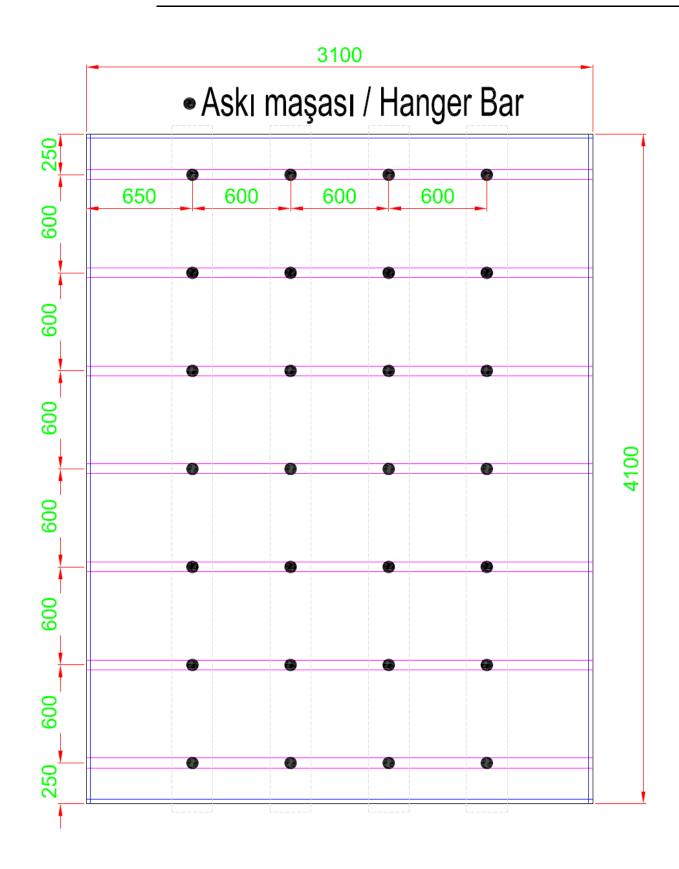


Figure 4: Location of hanger bars and TC profiles

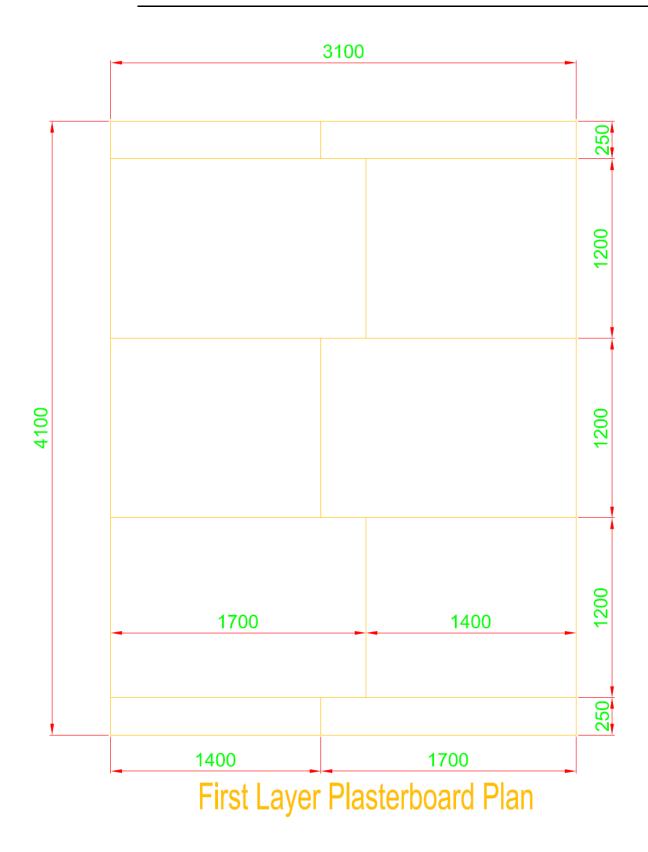


Figure 5: First (Inner) layer view of exposed side of the test specimen.

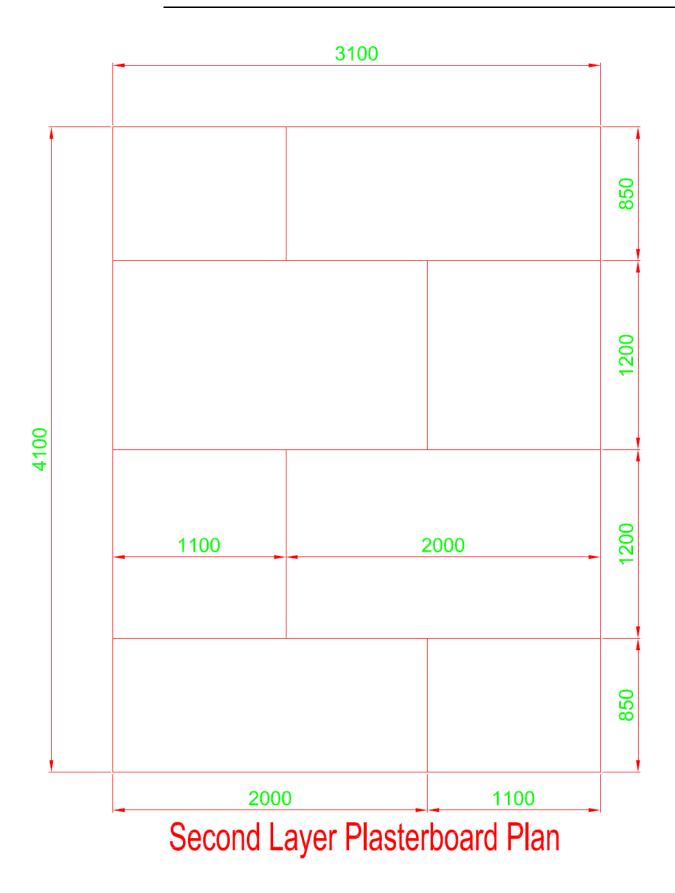


Figure 6: Second (Outer) layer view of exposed side of the test specimen.

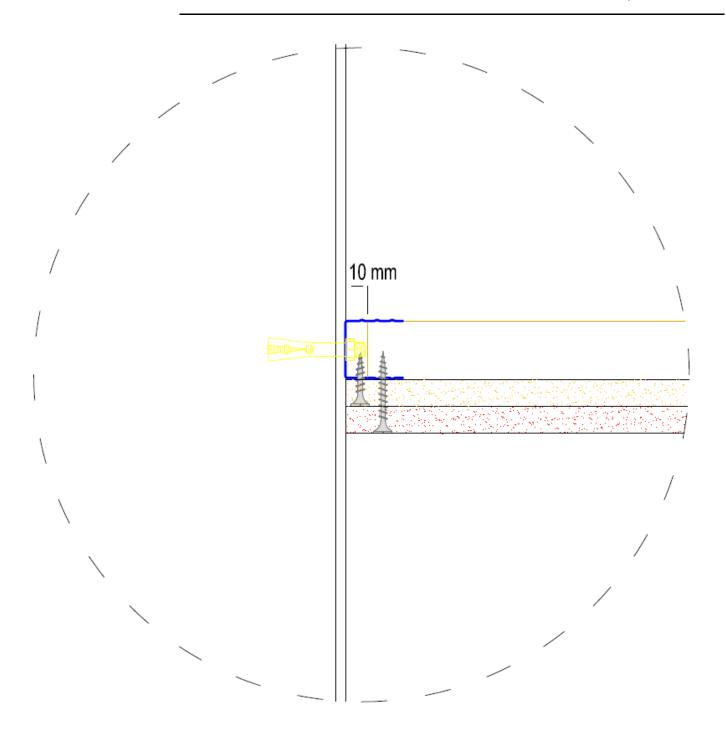


Figure 7: TC – TU steel profiles junction detail.

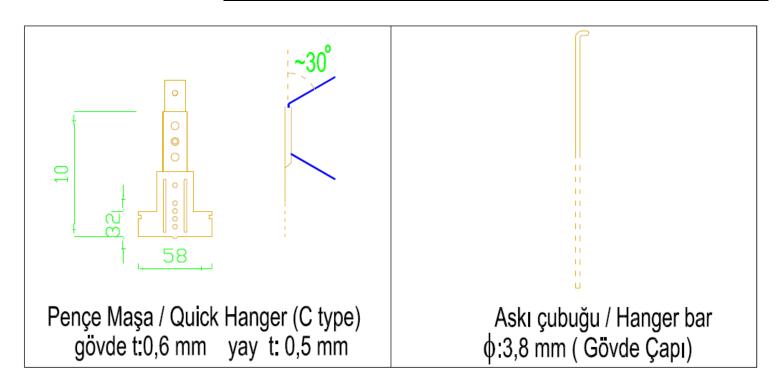


Figure 8: Quick hanger (C Type) details.